



THE GLOBAL STANDARD  
FOR LIVESTOCK DATA

# Section 10 - Appendix B5: Laboratory Test for Conventional Plastic Ear Tags

## Section 10 - Laboratory Test for Conventional Plastic Ear Tags

Version August 2024

Ref: 10-Appendix-B5-Laboratory-Test-for-Conventional-Plastic-Ear-Tags.docx

# Table of Contents

<b>1</b>	<b>Assessment of descriptive parameters</b>	<b>3</b>
1.1	Weight and dimensions	3
1.2	Composition	3
1.2.1	Characteristics of the ear tag plate plastic	3
1.2.2	Harmful substances	3
<b>2</b>	<b>Pre-conditioning of tag applicator</b>	<b>4</b>
<b>3</b>	<b>Pre-treatments</b>	<b>4</b>
3.1	Acid and alkaline bath treatment	4
3.2	Ageing by damp heat and cold	4
3.3	Resistance to artificial ageing	5
3.4	Abrasive Treatment	5
3.5	Introduction of samples into the climatic chamber	5
<b>4</b>	<b>Performance Assessment</b>	<b>5</b>
4.1	Typography readability	5
4.2	Evaluation of colour contrast change	6
4.3	Evaluation of contrast change for ear tags with combined laser and inkjet printing	6
4.4	Evaluation of machine readability (optional)	6
4.4.1	Barcode scanning	6
4.4.2	Barcode Print Quality Assessment	7
4.4.3	Evaluation of the resistance of the locking mechanism	7

## Change Summary

Date of Change	Nature of Change
August 2017	Updated Sections 1.2.2, 4.2, and 4.3.3 Replaced ISO 7724 with ISO 11664-4
October 2017	Corrected typographical errors Cross-references corrected
February 2018	Changes approved by the ICAR General Assembly.
September 2020	Added Section 3.1 Colour staining test Added Section 3.6 Introduction of samples into climatic chambers Updated Sections 3.2, 3.4, and 4.2
June 2021	Updated Section 4.4.3
May 2023	Added Section 2 Pre-conditioning of tag applicator Updated Sections 1.1, 3.1, 3.3, 3.5, and 4.3 Corrected grammatical errors Cross-references corrected
August 2024	Updated title page format

## 1 Assessment of descriptive parameters

The parameters describing the ear tag will be assessed and compared to the information provided in the Application Form to ensure accuracy of description.

### 1.1 Weight and dimensions

Ear tags shall have smooth, rounded corners and no sharp edges or protrusions especially on the shaft of the piercing pin. The following measurements will be taken:

- a. The dimensions of the front and rear plate (height, width and thickness)
- b. The pin (length and diameter)
- c. The weight of the complete locked ear tag
- d. The entrance hole of the cap
- e. The distance between the base of the pin and the base of the plate, i.e., the maximum possible distance between the inner side of the male and female components when the device is coupled, measured at the pin, with the two tag plates parallel with each other.

The results of these measurements will be compared to the Preliminary Assessment test report to ensure the accuracy of the samples.

### 1.2 Composition

Because ear tags are attached to "food producing" animals, they must meet specific requirements set down by international laws and regulations. In addition to these requirements, substances affecting animal, human or environmental health need to be detected. As such, certain chemical and physical composition traits of the ear tag will be evaluated. This evaluation will involve 20 ear tags.

#### 1.2.1 Characteristics of the ear tag plate plastic

To characterise the basic component of the plastic raw material, one ear tag plate is submitted to an Attenuated Total Reflectance-Fourier Transform Infrared (ATR-FTIR) spectroscopy analysis. Sample preparation is not necessary as the ear tag plate is pressed directly against the ATR-crystal. After analysis, the resulting ATR spectrum will be compared with characteristic spectra stored in specific databases.

Following this analysis, a material sample is submitted to a Differential Scanning calorimetry (DSC) analysis to analyse the thermal characteristics of the material as per ISO 11357. This analysis allows the detection of overlapping IR curves, e.g. if an additional component of minor quality was used to stretch the main component.

Melting point and glass transition temperatures are recorded to indicate the specific thermal characteristics of the plastic material.

#### 1.2.2 Harmful substances

Pigmented plastics may contain critical heavy metals which must be recorded. These metals are: Cadmium (Cd), lead (Pb), mercury (Hg) and chromium (Cr). If chromium is detected, an additional analysis of carcinogenic hexavalent chromium will be done. The following limit values must not be exceeded:

- a. Cadmium: 100 mg/kg
- b. Lead: 10 mg/kg

- c. Mercury: 1 mg/kg
- d. Chromate (Cr VI): < 1 mg/kg

## 2 Pre-conditioning of tag applicator

Devices requiring coupling for various testing procedures will be coupled in an environment of 21°C ± 2° and a relative humidity (RH) of 50% ± 10%. Before coupling, the supplied applicator and the devices will be preconditioned to this environment for a minimum period of 24 hours.

## 3 Pre-treatments

Various treatments are required to prepare tags for the testing of particular characteristics and are outlined in the following sections. These pre-treatments and ensuing performance assessments are summarized in the following table:

	New tags		UV/rain aged tags		Damp heat/cold aged tags
	Untreated	Acid / Alkaline bath	Untreated	Abraded	Untreated
Colour Staining	x				
Visual readability					
Typography	x		x	x	
Colour contrast	x		x		
Machine readability					
Barcode scanning	x	x	x	x	x
Barcode quality check	x				
Resistance of the locking mechanism	x		x		x

### 3.1 Acid and alkaline bath treatment

Three coupled ear tags are immersed for 3 weeks in a 21°C acid liquid (acetic acid, pH = 3) and another three coupled ear tags are immersed for 3 weeks in a 21°C alkaline liquid (sodium hydroxide, pH = 12). Both these treatments are to ensure compliance with ISO 175 for thermoplastics and ISO 1817 for vulcanized elastomers. As a reference, another three coupled ear tags are immersed in demineralized water for the same time period as the acid and alkaline baths.

These tests will only be done on ear tags where the tip and inner ring of the locking mechanism contain metal parts to ensure there is no susceptibility to galvanic corrosion.

After treatment, the samples are rinsed with demineralized water and dried for assessment of obvious deformation or material loss. Samples are also weighed before and after tests to detect material loss.

### 3.2 Ageing by damp heat and cold

In accordance with ISO 4611, 40 ear tags are placed into alternating cycles of 12 hours damp heat (40°C ± 2° / 95% RH) and 12 hours cold (-25°C ± 2°) for a duration of 3 weeks in a climatic chamber.

### 3.3 Resistance to artificial ageing

In accordance with EN ISO 4892-2, procedure A/cycle 1, 40 coupled ear tags are tested against resistance to sunlight. The exposure chamber will be fitted with xenon-arc lamps according to EN ISO 4892-2 and operated continuously for 1,000 hours. Due to the normal movement of animals' ears, both sides of a coupled ear tag are affected by the sun and other climatic elements. To simulate this process in the laboratory, ear tags undergoing an artificial aging testing within the climatic chamber are turned over after 500 hours. This ensures both sides of the coupled ear tag undergo 500 hours of exposure which has proven to be a sufficient time to assess aging behavior and to measure impacts on the material adequately. These 1,000 hours will consist of repeated cycles of 102 minutes of radiant exposure followed by 18 minutes of combined irradiation and rain simulation. The irradiance level of the xenon-arc lamps will be 60 W/m<sup>2</sup> (at 300-400 nm).


### 3.4 Abrasive Treatment

Five new, untreated ear tags and five artificially aged ear tags will be subjected to an abrasive treatment as per ISO 9352. These tags will receive 1500 cycles of abrasion in a 21°C ±2° laboratory environment.

The abrasive treatment uses CS17 abrasive wheels and a load of 1,000 g (or 9.8 N). The front plates of the tags are cut to a disc of about 100 mm in diameter and mounted on the test plate of the Taber Abrader.

### 3.5 Introduction of samples into the climatic chamber

To avoid irradiation of the stem and pin, the samples must be closed (coupled) with the manufacturer-supplied applicator, then spread apart and turned around so that male faces upwards and the female downwards, or vice versa. See pictures below:

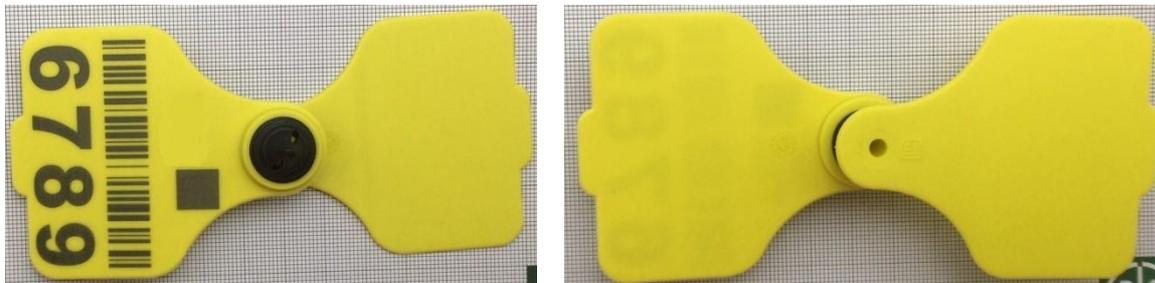

## 4 Performance Assessment

### 4.1 Typography readability

Five new, untreated tags and five tags from the following two treatment groups will be selected for assessment:

- a. Group 1: Artificially aged tags not subjected to the abrasive treatment.
- b. Group 2: Artificially aged tags subjected to the abrasive treatment.

Five randomly chosen numbers as given in [Appendix B3](#) will be printed on five white pages of paper. The font size, print style and character spacing will replicate that used for the ear tags.

The test tags and the pages with the printed numbers will be placed on a vertical surface (viewing surface) at head height in an appropriately lit laboratory room. Five assessors will

stand 15 metres from the viewing surface and then commence walking towards it. Each assessor will attempt to read the numbers on the different ear tags and pages and the distance at which each device (ear tag or page) can be read without error will be recorded on the evaluation sheet.

The mean reading distance for both the pages and the ear tags will be separately calculated for each assessor and for the average of the assessors.

The following requirements must be met:

- a. New, untreated tags: The mean distance at which the reference printing is read on the ear tags must be at least 80 % of the mean distance at which the pages are read.
- b. Artificially aged tags with and without the abrasive treatment: The mean distance at which the reference printing is read for the ear tags must be at least 65 % of the mean distance at which the pages are read.

#### **4.2 Evaluation of colour contrast change**

The colour difference of the ear tag plates and of the laser printing is measured and compared between three new ear tags and three artificially aged ear tags by use of spectral photometric measuring equipment according to ISO 11664-4.

After artificial ageing, the change in colour must be less than delta E\* of 15 CIELAB units.

#### **4.3 Evaluation of contrast change for ear tags with combined laser and inkjet printing**

Combined laser and inkjet printed tags can be tested as an additional option. If the option is chosen, then they will be tested in addition and parallel to laser printed tags only. If combined laser and inkjet printed tags will be tested, then ten tags with combined laser and inkjet printing shall be delivered in addition to the standard required quantity of laser printed tags for laboratory testing.

The tags printed with combined laser and inkjet printing will be subjected to the colour contrast change evaluation test before and after an abrasive treatment (see Appendix B5 Paragraph 3.5). The comparative evaluation will be against a new tag printed with laser only. The change in colour must not fade beyond a maximum colour change of  $\Delta E^* \leq 15$  CIELAB units.

#### **4.4 Evaluation of machine readability (optional)**

This evaluation will occur if the manufacturer requests the machine readability testing in the Application Form ([Appendix B1](#)).

For ear tags with linear barcodes, the "Quiet Zone" or margin at each end of the barcode must be at least 5mm. The height of the barcode must be at least 8mm.

##### **4.4.1 Barcode scanning**

The ear tags subjected to the Phase 3 treatments will be scanned with three different handheld barcode readers.

The treated ear tags will be scanned in sequence and after the initial ear tag is successfully read, the second tag is scanned until successfully read. Each ear tag will be scanned a maximum of four times. This procedure is repeated for each tag in the treatment group and after the last tag is scanned, the scanning is recommenced (Run 2) with the first tag. A total of 60 scans per treatment and reader type will be conducted to obtain sufficient data to assess performance.

The number of scans required to successfully read each tag (e.g. one, two, three or four) in each run is recorded.

The scanning success rate of tags from each treatment group is expressed in a percentage value and based on the number of scans required for a successful read. The performance of the tag is assessed against the minimum performance standards shown below:

No. of scans required	Proportion of tags successfully read at each scan
1	95 %
2	98 %
3	99.7 %

The scanning performance achieved for each treatment is included in the report.

#### 4.4.2 Barcode Print Quality Assessment

Print quality assessment will be undertaken on ten new, untreated tags using the protocols described below.

Using an ISO 15426-1 barcode verifier the linear barcodes are assessed for print quality according to ISO 15416. Every ear tag will be scanned ten times to build average grades.

An ANSI scale of A (highly satisfactory) to F (unsatisfactory) will be used to grade the print quality for each characteristic. When determining the overall print quality, the final score for the code on a tag is the worst grade recorded for any of the assessed characteristics. Failure reasons will be given in the test report.

The following linear barcode print quality specifications must be met:

- a. Decode (the only grades used are A and F): A
- b. Decodability: minimum D meaning >25%
- c. Check Character (if available): OK
- d. Symbol Contrast (Rmax - Rmin): minimum D meaning >25%

In the print contrast component of the test for 2D barcodes, the QR code and DM symbols are assessed for print quality using a barcode verifier that complies with the AIM International standards, Section "M" under Matrix Code Print Quality Guideline.

The following 2D barcode print quality specifications must be met:

- a. Decode (the only grades used are A and F): A
- b. Symbol contrast: minimum D, meaning >25%
- c. Print growth X axis and Y axis: A/A, A/B or B/A
- d. Axial non-uniformity: A

The standard of symbols must be no more than one print quality grade below that for each parameter on an unused tag without treatment.

#### 4.4.3 Evaluation of the resistance of the locking mechanism

The ear tags are pre-conditioned for at least 2 hours before testing at the respective temperature. Testing must occur within 10 seconds after the ear tag is removed from the chamber.

30 new, untreated ear tags, 30 artificially aged ear tags and 30 ear tags submitted to the damp heat and cold treatment will be subjected to increasing forces to determine the force required to cause breakage or unfastening of the ear tag.

For cattle, sheep and goat ear tags, the test is performed at  $-25^{\circ}\text{C}$  ( $\pm 2^{\circ}$ ),  $21^{\circ}\text{C}$  ( $\pm 2^{\circ}\text{C}$ ) and  $55^{\circ}\text{C}$  ( $\pm 2^{\circ}\text{C}$ ) combined with 50% RH (when the temperature is higher than  $0^{\circ}\text{C}$ ) with 10 ear tags from the three treatment variations.

For pig ear tags, the test is performed at  $-10^{\circ}\text{C}$  ( $\pm 2^{\circ}$ ),  $21^{\circ}\text{C}$  ( $\pm 2^{\circ}$ ) and  $55^{\circ}\text{C}$  ( $\pm 2^{\circ}$ ) combined with 50% RH (when the temperature is higher than  $0^{\circ}\text{C}$ ) with 10 ear tags from the three treatment variations.

For tags which are used for both sheep/goat and pigs, the test is performed at  $-25^{\circ}\text{C}$  ( $\pm 2^{\circ}$ ),  $-10^{\circ}\text{C}$  ( $\pm 2^{\circ}$ ),  $21^{\circ}\text{C}$  ( $\pm 2^{\circ}\text{C}$ ), and  $55^{\circ}\text{C}$  ( $\pm 2^{\circ}\text{C}$ ) combined with 50% RH (when the temperature is higher than  $0^{\circ}\text{C}$ ) with 10 ear tags from the three treatment variations.

The forces will be applied at a rate of 500 mm/min within 10 seconds after the tags are removed from the climatic chamber. The force applied to cause breakage or unfastening of each ear tag will be recorded.

**Requirements:**

- a. None of the ear tags – neither male nor female part – must be re-usable. Male pin tips must break off and remain within the female caps (locking gap).
- b. At  $21^{\circ}\text{C}$  ( $\pm 2^{\circ}\text{C}$ ), no breakage should occur in:
  - Tags designed to be used in cattle with the application of a force lower than 280 Newton.
  - tags designed to be used in sheep and / or goats with the application of a force lower than 200 Newton.
  - tags designed to be used in pigs with the application of a force lower than 200 Newton.
- c. The minimum breaking force applies to devices irrespective of treatments (artificial ageing, damp heat and cold).

Additionally, the distortion occurring in the ear tag at the time of breakage or unfastening will be recorded during the tensile tests as an indicator for any changes in the mechanical properties of the plastic after exposure to the artificial ageing and the damp heat/cold treatments.